
EFFECT OF ZIGZAG AND LINE PRINTING PATTERN ON TENSILE STRENGTH AND SURFACE ROUGHNESS OF FUSED DEPOSITION MODELING PRODUCT

Ayu Perwita Sari

Faculty of Engineering, Department of Mechanical Engineering
Universitas Muhammadiyah Surakarta
Email: ayuperwitasari1803@gmail.com

Fatkur Rhozman

Faculty of Engineering, Department of Mechanical Engineering
Universitas Muhammadiyah Surakarta
Email: U100220014@student.ums.ac.id

Ayis Nuredi Winata

Faculty of Engineering, Department of Mechanical Engineering
Universitas Muhammadiyah Surakarta
Email: U100220009@student.ums.ac.id

Frendy Edo Herlanto

Faculty of Engineering, Department of Mechanical Engineering
Universitas Muhammadiyah Surakarta
Email: U100220011@student.ums.ac.id

Abdul Munir Hidayat Syah Lubis

Faculty of Engineering, Department of Mechanical Engineering
Universitas Muhammadiyah Surakarta
Email: amh612@ums.ac.id

Agus Dwi Anggono

Faculty of Engineering, Department of Mechanical Engineering
Universitas Muhammadiyah Surakarta
Email: agus.d.anggono@ums.ac.id

ABSTRAK

Penelitian ini bertujuan untuk menguji hasil 3D printing yang menggunakan filamen jenis *Polylactic acid* (PLA) terhadap kekasaran permukaan dan kekuatan tarik. Eksperimen dilakukan dengan mengatur perbedaan kerapatan pengisian pencetakan terhadap pola yang digunakan. Kerapatan pengisian menggunakan variasi 60%, 80% dan 100%. Uji Tarik digunakan untuk mengukur sifat mekanik tarik polimer (σ). Uji kekasaran diperoleh untuk mengetahui kekasaran permukaan rata-rata (R_a), root mean square roughness (R_q), ten-point height (R_z). Specimen pengujian menggunakan model dan ukuran standar ASTM D638 type 4. Diameter nozzle 0,4 mm, suhu 220 °C, dan suhu heat bed sebesar 60 °C. Hasil uji sifat mekanik dari pola percetakan diperoleh bahwa pola zigzag memiliki nilai *yield strength*, *maximum load* dan *elongation* tertinggi yaitu sebesar 0,97 N/mm², 52,99 N dan 9,43%. Sedangkan pada pola line nilai *yield strength*, *maximum load* dan *elongation* tertinggi yaitu sebesar 1,51 N/mm², 62,72 N, dan 3,54% dan hasil tertinggi dari kedua pola adalah pada pola percetakan tertinggi yaitu 100%. Diperoleh kesimpulan bahwa semakin besar pola percetakan maka akan mempengaruhi ukuran lebar dari filamen akibatnya tingkat kekasaran permukaan juga semakin tinggi.

Kata kunci: 3D Printing, *Polylactic acid* (PLA), Pola Pengisian, Uji Tarik

ABSTRACT

This research aims to test the results of 3D printing using Poly lactic acid (PLA) filament on surface roughness and tensile strength. Experiments were carried out by adjusting the differences in printing fill density for the pattern used. Filling density uses variations of 60%, 80%, and 100%. The tensile test is used to measure the tensile mechanical

properties of polymers (σ). The roughness test is obtained to determine the average surface roughness (R_a), root mean square roughness (R_q), and ten-point height (R_z). The test specimen uses the ASTM D638 type 4 standard model and size. The nozzle diameter is 0.4 mm, the temperature is 220 °C, and the heat bed temperature is 60 °C. The mechanical properties test results of the printing pattern showed that the zigzag pattern had the highest yield strength, maximum load, and elongation values, namely 0.97 N/mm², 52.99 N, and 9.43%. Meanwhile, in the line pattern, the highest yield strength, maximum load, and elongation values were 1.51 N/mm², 62.72 N, and 3.54% and the highest yield of the two patterns was in the highest printing pattern, namely 100%. It was concluded that the larger the printing pattern, the wider the filament will be, as a result the level of surface roughness will also be higher.

Keywords: 3D Printing, Poly Lactic Acid (PLA), Filling Pattern, Tensile Test

1. INTRODUCTION

3D Printing is an additive manufacturing (AM) process for creating 3D objects with processes that are carried out in layers. 3D object printing is done by reading 3D designs that have been made on computer software such as computer-aided design (CAD)[1]. This technology is widely developed in manufacturing techniques because it has high flexibility in determining the model with less material waste. thus the use of materials is more efficient than other manufacturing processes [2]. In general, the application of 3D printing technology is now increasingly widespread to be used in various sectors such as manufacturing, automotive, industry, medicine, construction, and many other applications [3].

In its development, 3D printing uses a variety of techniques according to the type of material used. The most popular additive manufacturing (AM) process technique approaches are currently the utilized of fused deposition modeling (FDM) [4][5]. The advantages of this FDM technique are the simple fabrication process, more cost-effective production, and environmentally friendly [6][7]. On the other hand, it also has disadvantages such as limited accuracy, relatively slow production process speed, and shrinkage due to temperature changes [8].

Filament materials used in additive manufacturing processes have various types with special specifications that are adjusted based on their application. The types of filaments commonly used in 3D printing technology are Acrylonitrile Butadiene Styrene (ABS), Polycarbonate (PC), and Poly Lactic Acid (PLA) polyamide 12 (PA12) [9]. Poly Lactic Acid (PLA) is the most widely used type of filament in 3D printing technology [10]. PLA filament is also a bio-degradable filament because it comes from lactic acid synthesized from natural materials and has elastic properties and a high tensile modulus [11][12]. The use of PLA for manufacturing additives (AM) materials in FDM techniques can improve the physical, mechanical, and thermal properties of 3D printed composites [13].

B.M. Tymrak et al conducted research on the mechanical properties of 3D printing with the development of the RepRap method on Poly Lactic Acid (PLA) filaments and Acrylonitrile Butadiene Styrene (ABS) obtained the results that Poly Lactic Acid (PLA) has a tensile strength value of 56.6 MPa and a modulus of elasticity of 33.68 MPa so that the bond between layers is very strong, so it works more rigidly. While ABS has a tensile strength value of 28.5 MPa and a modulus of elasticity of 1807 MPa [14]. Rodriguez et al conducted research using Poly Lactic Acid (PLA) filaments and Acrylonitrile Butadiene Styrene (ABS) with the Fused Deposition Modeling (FDM) additive manufacturing technique method. In the study, it was found that Poly Lactic Acid (PLA) is more rigid and has greater tensile strength than Acrylonitrile Butadiene Styrene (ABS) so this type of filament is more suitable for use in the additive manufacturing process [15].

Samarthya Bhagia et al researched 3D printing by fused deposition modeling (FDM) with Poly Lactic Acid (PLA) filament made from biomass. The study was conducted to determine the effect of FDM printing on the results of 3D printing objects using PLA filaments. The result is that FDM printing affects the surface characteristics of the printing result. In addition, other factors such as nozzle printing temperature, Filling Pattern, and pattern manufacturing can also affect the quality of the printing results [16].

Benoît Pernet et al examined the influence of 3D printing pattern geometry with ASTM D695 using Poly Lactic Acid (PLA) material in FDM printing models. The results of the study obtained that the printing pattern affects printing time and can reduce production costs. However, this study has not discussed the test of the resulting printing pattern [17]. Lactic acid is a source of biodegradable filaments known as PLA and is the most popular material for 3D printing processes involving material extrusion. In addition, the advantage of PLA filament is that it is easy to use in 3D printing because it has strength and does not suffer from major distortion when printing due to the low extrusion temperature (melting point) [18][19]. The selection of thermoplastic materials (filaments) is very important, as each commercially available thermoplastic filament has different physical, thermal, chemical, rheological, and mechanical properties. Therefore, this study aims to conduct experiments on the mechanical properties of 3D printing with Poly Lactic Acid (PLA) filament material as a basis before being applied more widely. The parameters used are the roughness test and

tensile test to determine the mechanical properties of 3D printed specimens by varying the printing pattern nozzle temperature, and Filling Pattern.

2. MATERIAL AND METHODS

This study uses PLA-type filaments that have a diameter of 1.75 mm. The specimen was made with a commercial 3D printing machine, Ender-5Plus, which has reality slicer software used to control the settings of the 3D printing process and exports the 3D design file for reading with a G-code compatible with the manufacturer's machine. The filament is printed using a nozzle of diameter 0.4 mm at a temperature of 220 °C with a heat bed at a temperature of 60 °C. It is clearly seen in Figure 1.

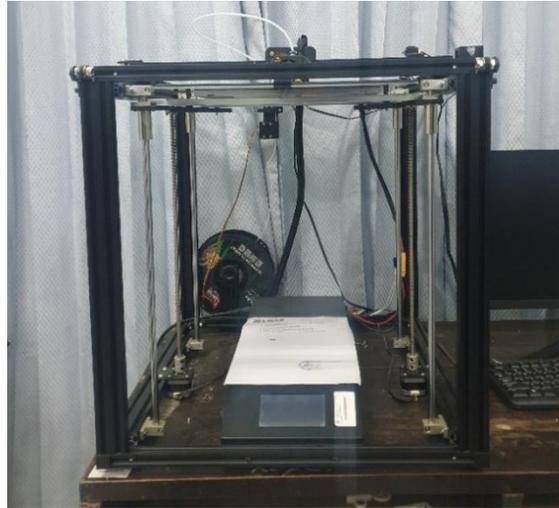


Figure 1. 3D Printing Ender-5 Plus

A tensile testing machine (Gotech Testing - AI - 7000 L, Taiwan) is used to measure the tensile mechanical properties of polymers. Tests were conducted to determine the effect of 3D printing parameters (print orientation and Filling Pattern) on tensile strength (σ). It is clearly seen in Figure 2.



Figure 2. Gotech Testing-AI-7000 L

Roughness test on 3D printed specimens (Mitutoyo roughness test tool) is carried out in three parts on each test specimen to then be averaged. The roughness test results are to obtain parameters of average surface roughness (Ra), root means square roughness (Rq), and ten-point height (Rz).

The 3D design of the test specimen followed the ASTM D638 type 4 standard [20][21]. Shown in Figure 3 are the sketch drawings made using CAD software, namely CATIA, print orientation is done with two patterns, that is, zigzag printing patterns, and line printing patterns. Filling Pattern is one of the parameters that is set before the slicer process in 3D printing. In this research the specimens were printed with filling of 60%, 80%, and 100% at nozzle temperature of 220°C.

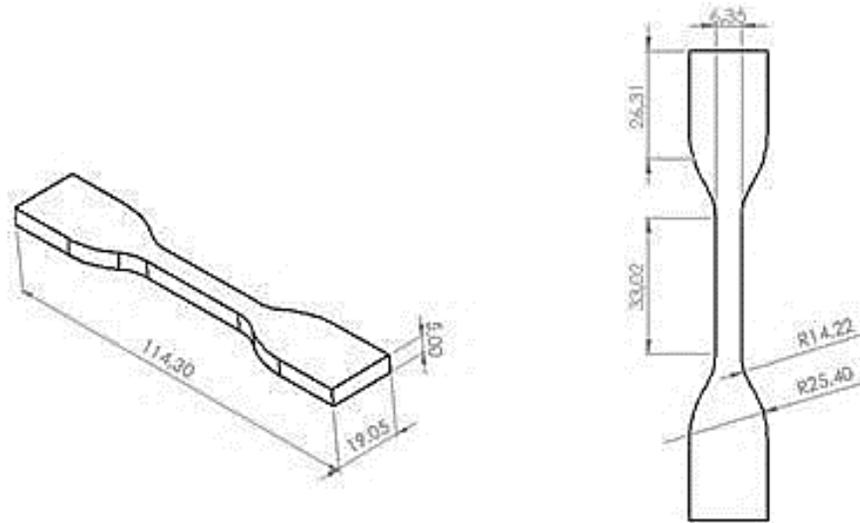


Figure 3. Design of the 3D Printed Specimen

3. RESULTS AND DISCUSSION

3.1 Specimen Prints

The 3D printing specimens that have different printing patterns, namely zigzag patterns and line patterns with Filling Patterns of 60%, 80%, and 100% shown in Figure 4 were tested for surface roughness and tensile mechanical properties.

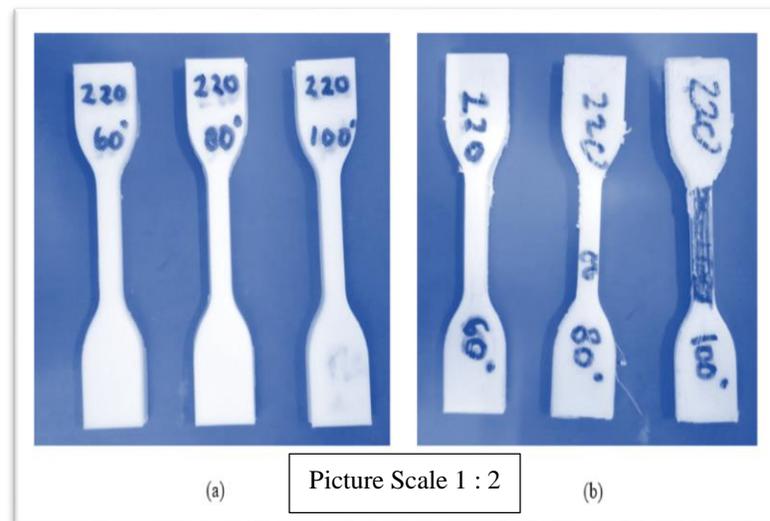


Figure 4. (a) Zigzag Pattern Specimen (b) Line Pattern Specimen

3.2 Microstructure characteristics

The Microstructure characteristics of the specimen printed by the 3D printing test in Figure 5 show the Microstructure characteristics test results of the impact of filament pattern and Filling Pattern on filament width. The prints with Filling Patterns of 60%, 80%, and 100% in the zigzag pattern have an average filament width of 512.33 μm , 515.33 μm and 521 μm . With the same Filling Pattern, the line pattern has an average filament width of 497 μm , 524.33 μm , and 597 μm . The results show the similarity of the two filaments, namely the increase in filament width as the Filling Pattern increases. This happens because the higher the Filling Pattern will cause the cooling time on the filament to be faster [22].

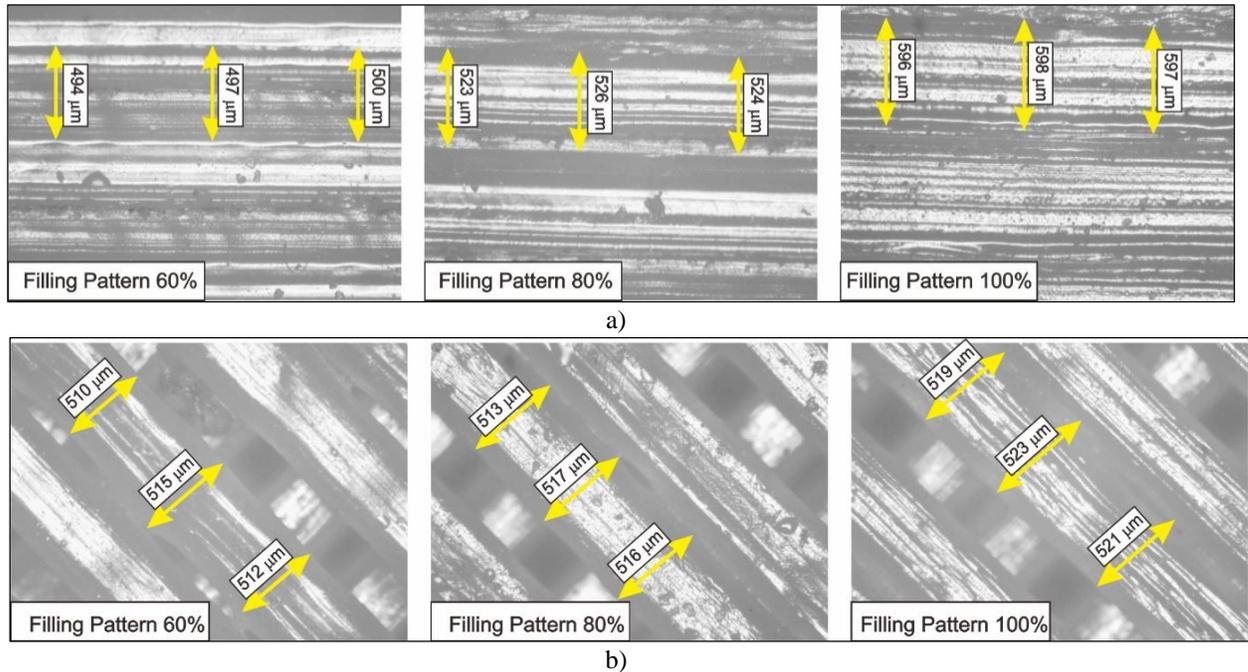


Figure 5. (a) Line Pattern (b) Zigzag Pattern

3.3 Surface Roughness Test

After testing the surface roughness average (R_a) and root mean square roughness (R_q) of specimens with zigzag patterns and line patterns, significant differences in results were obtained. The influence of higher Filling Pattern makes the surface roughness average (R_a), and root mean square roughness (R_q) increase and this to be rougher. This significant difference in roughness values is seen between the zigzag pattern and the line pattern. Of the three variations of Filling Pattern used, the lowest value is at the Filling Pattern of 60%, the average value obtained in the zigzag pattern is 20,37 μm while in the line pattern is 11,24 μm . This also occurs in root mean square roughness (R_q) where the zigzag pattern has a higher value than the line pattern, which is 26,29 μm and 14,74 μm respectively. These are depicted in Figures 6 and 7 as follows:

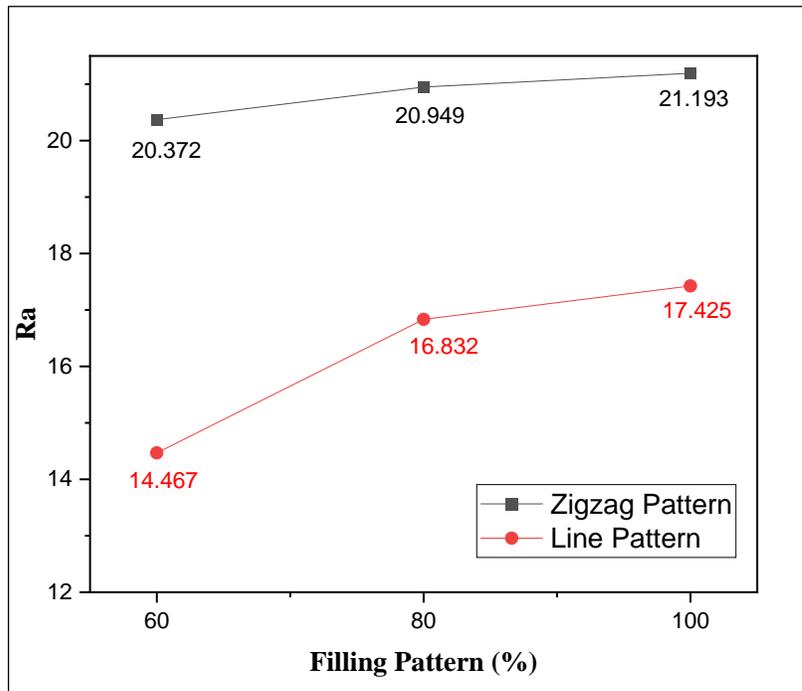


Figure 6. Graph of average Roughness (Ra) (μm)

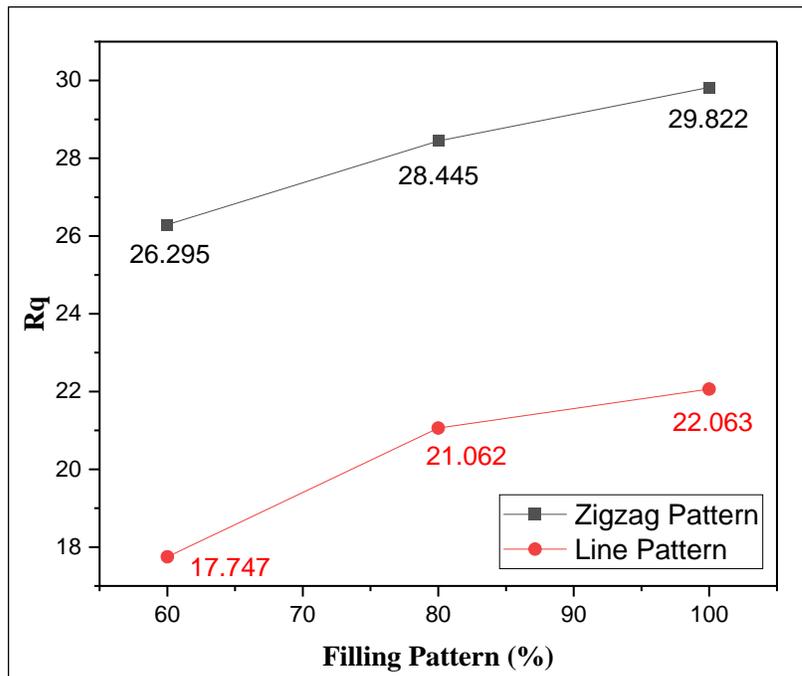


Figure 7. Graph of Root Mean Square roughness (Rq) (μm)

Figure 8 depicts a graph illustrating the average maximum height of the profile (Rz), representing the peak length and maximum valley depth. The graph demonstrates an increase in roughness values as the Filling Pattern rises, displaying zigzag patterns and line patterns. At a Filling Pattern of 100%, the zigzag pattern and line pattern exhibit the highest average maximum height of the profile (Rz) values, which are 121.76 μm and 93.25 μm respectively.

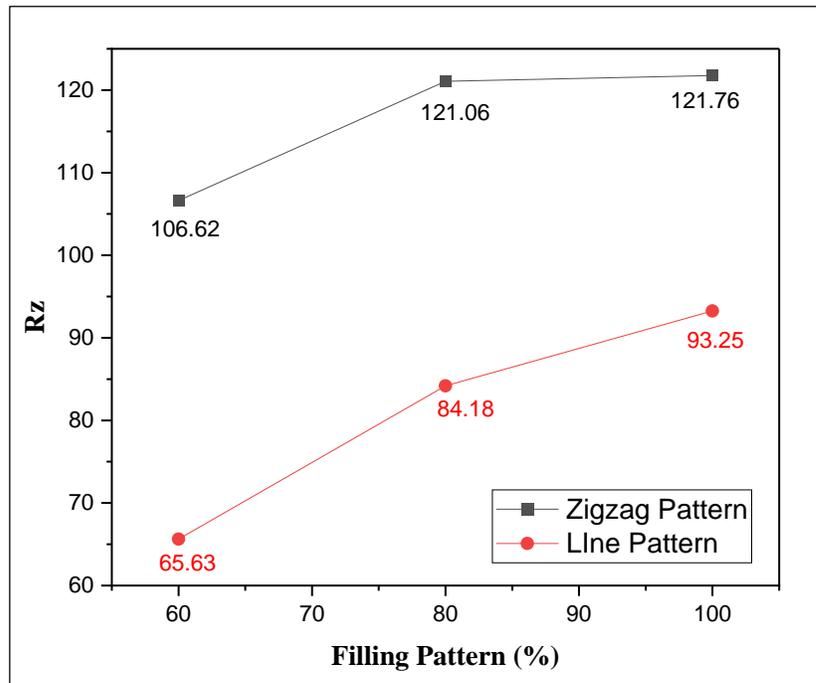


Figure 8. The ten-point height value (Rz) (μm)

3.4 Tensile Test and Microstructure Characteristics

Figure 9 presents the visual representation of the specimens after undergoing a tensile test. The impact of printing patterns on Poly Lactic Acid (PLA) tensile test values is detailed in Table 1. Comparing the tensile test results of the specimen print patterns, it was observed that the zigzag pattern yielded higher values compared to the line pattern. Additionally, when the specimen was printed using zigzag patterns and line patterns at Filling Patterns of 60%, 80%, and 100%, there was not a significant increase in yield strength. However, a significant disparity is observed in the elongation value between the zigzag pattern and the line pattern. It has been determined that the average elongation value in the line pattern is only 50% of the elongation value observed in the zigzag pattern. This indicates a substantial difference in the ability of the two patterns to withstand elongation without fracturing or breaking. This is by Hooke's law where the relationship between a given force and a change in length is directly proportional. Another significant cause of the difference is that the mold direction line pattern is perpendicular to the applied load, so it has a brittle failure and lower tensile strength compared to the zigzag printing pattern. Other parameters such as the value of modulus of elasticity in the specimen printing pattern decrease as the Filling Pattern increases. The maximum load value with a zigzag pattern with a Filling Pattern of 60%, 80%, and 100% obtained values of 48.38 N, 49.14 N, and 52.99 N while in the line pattern with the same parameters obtained values of 59.07 N, 59.88 N, and 62.72 N. So, it can be concluded that there is an enhancement in the maximum tensile stress value in both types of specimens which is directly proportional to the Filling Pattern.

Table 1. Tensile test result data

Pattern Variations	Filling Percentage (%)	Yield Strength (N/mm ²)	Elongation (%)	Elastic Modulus (N/mm ²)	Maximum Load (N)
PLA Zigzag	60%	0.92	6.76	197.02	48.38
	80%	0.93	6.98	178.15	49.14
	100%	0.97	9.43	151.40	52.99
PLA Line	60%	1.15	2.79	134.21	59.07
	80%	1.05	3.00	127.01	59.88
	100%	1.51	3.54	94.30	62.72

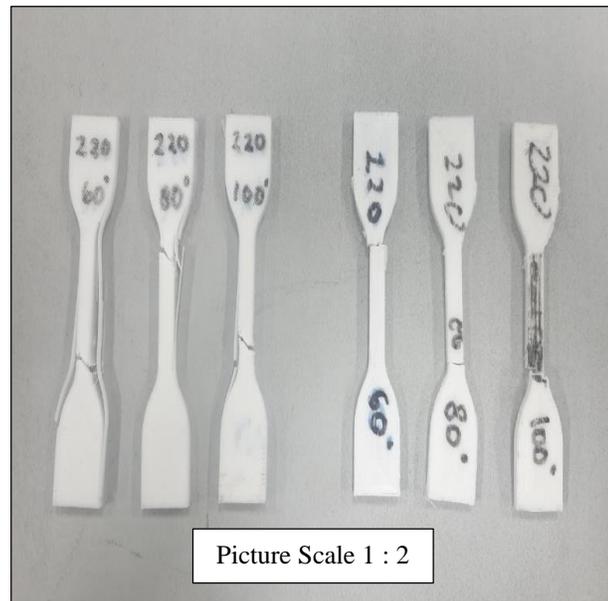


Figure 9. Specimens after the tensile test

4. CONCLUSION

Based on the test study, the conclusions drawn regarding Poly Lactic Acid (PLA) specimen printing using the fused deposition modelling (FDM) method with different printing patterns. The result of the mechanical properties related to tensile strength, such as yield strength and maximum load, tend to increase as the Filling Pattern rises. This implies that higher Filling Patterns result in stronger PLA specimens. The research observed that as the Filling Pattern increases, the surface roughness of the printed PLA specimens becomes more pronounced. This means that higher Filling Patterns result in a larger surface roughness value, indicating a rougher surface texture. This shows that the correlation between surface roughness and mechanical properties of tensile tests is directly proportional.

REFERENCES

- [1] S. Bose, D. Ke, H. Sahasrabudhe, and A. Bandyopadhyay, "Additive manufacturing of biomaterials," *Prog. Mater. Sci.*, vol. 93, pp. 45–111, 2018, doi: 10.1016/j.pmatsci.2017.08.003.
- [2] D. K. Lee *et al.*, "Fabrication of 3D structure with heterogeneous compositions using an inkjet printing process," *Mater. Today Commun.*, vol. 35, no. February, p. 105753, 2023, doi 10.1016/j.mtcomm.2023.105753.
- [3] T. P. Mpofo, C. Mawere, and M. Mukosera, "The Impact and Application of 3D Printing Technology," *Int. J. Sci. Res.*, vol. 3, no. 6, pp. 2148–2152, 2014, [Online]. Available: https://www.academia.edu/download/34056587/MDIwMTQ2NzU_.pdf%0Ahttps://www.researchgate.net/publication/291975129
- [4] R. Winarso, P. W. Anggoro, R. Ismail, J. Jamari, and A. P. Bayuseno, "Application of fused deposition modeling (FDM) on bone scaffold manufacturing process: A review," *Heliyon*, vol. 8, no. 11, p. e11701, 2022, doi: 10.1016/j.heliyon.2022.e11701.
- [5] A. Ramya and S. L. Vanapalli, "3D printing technologies in various applications," *Int. J. Mech. Eng. Technol.*, vol. 7, no. 3, pp. 396–409, 2016.
- [6] Y. Zhao, Y. Chen, and Y. Zhou, "Novel mechanical models of tensile strength and elastic property of FDM AM PLA materials: Experimental and theoretical analyses," *Mater. Des.*, vol. 181, p. 108089, 2019, doi: 10.1016/j.matdes.2019.108089.

- [7] T. N. A. T. Rahim, A. M. Abdullah, and H. Md Akil, "Recent Developments in Fused Deposition Modeling-Based 3D Printing of Polymers and Their Composites," *Polym. Rev.*, vol. 59, no. 4, pp. 589–624, 2019, doi 10.1080/15583724.2019.1597883.
- [8] B. Road, "A Review : Fused Deposition Modeling – a Rapid Prototyping Process," *Int. Res. J. Eng. Technol.*, vol. 4, no. 9, pp. 5–9, 2017, [Online]. Available: <https://irjet.net/archives/V4/i9/IRJET-V4I989.pdf>
- [9] Q. Wang *et al.*, "Efficient characterization on the interlayer shear strengths of 3D printing polymers," *J. Mater. Res. Technol.*, vol. 22, pp. 2768–2780, 2023, doi: 10.1016/j.jmrt.2022.12.147.
- [10] L. Marşavina *et al.*, "Effect of the manufacturing parameters on the tensile and fracture properties of FDM 3D-printed PLA specimens," *Eng. Fract. Mech.*, vol. 274, no. August, 2022, doi: 10.1016/j.engfracmech.2022.108766.
- [11] G. Zhang *et al.*, "A systematic investigation on the minimum tensile strengths and size effects of 3D printing polymers," *Polym. Test.*, vol. 117, no. October 2022, p. 107845, 2023, doi: 10.1016/j.polymertesting.2022.107845.
- [12] A. Pappu, K. L. Pickering, and V. K. Thakur, "Manufacturing and characterization of sustainable hybrid composites using sisal and hemp fibers as reinforcement of poly (lactic acid) via injection molding," *Ind. Crops Prod.*, vol. 137, no. November 2018, pp. 260–269, 2019, doi 10.1016/j.indcrop.2019.05.040.
- [13] L. P. Muthe, K. Pickering, and C. Gauss, "A Review of 3D/4D Printing of Poly-Lactic Acid Composites with Bio-Derived Reinforcements," *Compos. Part C Open Access*, vol. 8, no. April, p. 100271, 2022, doi 10.1016/j.jcomc.2022.100271.
- [14] B. M. Tymrak, M. Kreiger, and J. M. Pearce, "Mechanical properties of components fabricated with open-source 3-D printers under realistic environmental conditions," *Mater. Des.*, vol. 58, pp. 242–246, 2014, doi: 10.1016/j.matdes.2014.02.038.
- [15] A. Rodríguez-Panes, J. Claver, and A. M. Camacho, "The influence of manufacturing parameters on the mechanical behavior of PLA and ABS pieces manufactured by FDM: A comparative analysis," *Materials (Basel)*, vol. 11, no. 8, 2018, doi: 10.3390/ma11081333.
- [16] S. Bhagia *et al.*, "Critical review of FDM 3D printing of PLA biocomposites filled with biomass resources, characterization, biodegradability, upcycling and opportunities for biorefineries," *Appl. Mater. Today*, vol. 24, 2021, doi: 10.1016/j.apmt.2021.101078.
- [17] B. Pernet, J. K. Nagel, and H. Zhang, "Compressive Strength Assessment of 3D Printing Infill Patterns," *Procedia CIRP*, vol. 105, no. March, pp. 682–687, 2022, doi: 10.1016/j.procir.2022.02.114.
- [18] E. Petersen, R. Kidd, and J. Pearce, "Impact of DIY Home Manufacturing with 3D Printing on the Toy and Game Market," *Technologies*, vol. 5, no. 3, p. 45, 2017, doi: 10.3390/technologies5030045.
- [19] P. M. Angelopoulos *et al.*, "Manufacturing of ABS/expanded perlite filament for 3D printing of lightweight components through fused deposition modeling," *Mater. Today Proc.*, vol. 54, no. xxxx, pp. 14–21, 2021, doi: 10.1016/j.matpr.2021.06.351.
- [20] T. Method and T. Note, "ASTM D638 Tensile Properties of Plastics TEST METHOD SUMMARY Pneumatic Vise Grips Manual Wedge Grips Screw Action Grips Manual Vise Grips Serrated Grip Faces Diamond Tip Faces Flat Rubber Faces", [Online]. Available: www.mts.com
- [21] P. Materials, E. I. Materials, P. Matrix, C. Materials, and P. Specimens, "Standard Test Method for Tensile Properties of Plastics 1," no. January 2004, pp. 1–15, 2006, doi: 10.1520/D0638-14.
- [22] A. A. Samy, A. Golbang, E. Harkin-Jones, E. Archer, D. Tormey, and A. McIlhagger, "Finite element analysis of residual stress and warpage in a 3D printed semi-crystalline polymer: Effect of ambient temperature and nozzle speed," *J. Manuf. Process.*, vol. 70, no. June, pp. 389–399, 2021, doi: 10.1016/j.jmapro.2021.08.054.